

Characterisation of organic colourants in *ukiyo-e* prints by Fourier transform near infrared fibre optics reflectance spectroscopy

C. Biron,^{a,b*} F. Daniel,^a G. Le Bourdon,^b R. Chapoulie^a and L. Servant^b

^aUniversité Bordeaux Montaigne, IRAMAT-CRP2A – UMR CNRS 5060, Maison de l'Archéologie, Esplanade des Antilles, 33607 Pessac cedex, France.

E-mail: carole.biron@u-bordeaux-montaigne.fr

^bUniversité de Bordeaux, Institut des Sciences Moléculaires – UMR 5255, Bâtiment A12 351 Cours de la Libération, 33405 Talence cedex, France

The materials used in Japanese woodblock prints called *ukiyo-e*, particularly colouring matters, function as indicators on the resources available at a given time and allow us to deepen our knowledge of the cultural purposes and the socio-economic (trading activity, import of new techniques...) impacts of these artworks. The aim of this work is to apply non-invasive near infrared (NIR) spectroscopy which may be helpful for the identification of organic colourings widely employed in *ukiyo-e*, using fibre optics such as the Fibre Optics Reflectance Spectroscopy (FT-NIR FORS), that has been applied to the cultural heritage field for two decades because of its fast response time in any geometrical configuration. The present work reports results obtained on five organic pigments (indigo, safflower, gamboge, dragon's blood and cochineal), considered as the first step for the building of a database dedicated to specific Japanese colouring matters in order to interpret future hyperspectral data recorded in the Short Wave InfraRed (SWIR) range on a collection of Japanese *ukiyo-e* prints. The data were obtained with a FT-NIR spectrometer using a probe to collect the specular reflection within the 11,000–4000 cm⁻¹ range, transformed in pseudo-absorbance with log(1/R) conversion. Because large bands were observed, originating in overtone and combination modes, a pre-processing smoothing and derivative procedure of the data, together with Principal Component Analysis (PCA) were applied to discriminate the pigments, notably dragon's blood.

Introduction

For several years, the study of paintings enables us to improve our knowledge on the materials (pigments, binders, substrate) and techniques used by the artists in terms of cultural or socio-economic issues (trade exchanges, importation of new technologies...). However, analyses are often constrained by the fragility of the painted artworks, such as prints, and by curators who forbid any sampling or any move of the artworks out of the museum. Regarding these issues and the various materials used through times, adapted analytical strategies using non-invasive and contactless methods have been developed to investigate painted artworks.^{1–5} Infrared spectroscopy is a selective and sensitive method that is in principle able to evidence most of the materials used in paintings. Since the 2000s, infrared reflectance spectroscopy has been applied to

the identification of pigments, dyes and binders using various Fourier Transform Infrared spectroscopy (FTIR) sampling techniques in the mid-infrared range.^{6–8} More recently, near infrared (NIR) reflectance spectroscopy has also been applied thanks to the use of fibre optics (Fibre Optics Reflectance Spectroscopy – FORS)^{9–13} and allows non-invasive analyses with a fast response time in any geometrical configuration.

The aim of this study is to develop and apply portable NIR spectroscopy for the non-invasive probing of organic colourings employed in the Japanese prints, or *ukiyo-e*, of the Federico Torralba collection, currently kept in the Museum of Zaragoza, Spain. Japanese *ukiyo-e* works refer to woodblock prints or paintings produced between the 17th and the late 19th century during the Edo (1615–1868) and the Meiji (1868–1912) eras.

Correspondence

C. Biron (carole.biron@u-bordeaux-montaigne.fr)

doi: 10.1255/nir2017.015

Citation: C. Biron, F. Daniel, G. Le Bourdon, R. Chapoulie and L. Servant, "Characterisation of organic colourants in *ukiyo-e* prints by Fourier transform near infrared fibre optics reflectance spectroscopy", in Proc. 18th Int. Conf. Near Infrared Spectrosc., Ed by S.B. Engelsen, K.M. Sørensen and F. van den Berg, IM Publications Open, Chichester, pp. 15–22 (2019). <https://doi.org/10.1255/nir2017.015>

© 2019 The Authors

This licence permits you to use, share, copy and redistribute the paper in any medium or any format provided that a full citation to the original paper is given, the use is not for commercial purposes and the paper is not changed in any way.



ISBN: 978-1-906715-27-4

The Federico Torralba collection brings together more than a thousand Asian works of art. Among them, there are a hundred *ukiyo-e* signed by some of the greatest Japanese artists such as Utamaro, Hiroshige or Hokusai. Beyond the possibility to assess the state of conservation and degradation of the prints of the collection, the analyses conducted on these artworks aim at improving our knowledge on the history of art and on preparation techniques of the *ukiyo-e* by identifying the matters (nature, composition...) involved in their productions. The materials used, particularly colouring matters, constitute indicators on the typical resources available at a given period and allow us to deepen our knowledge on the technical, aesthetic or economic choices (for example natural or synthetic pigments, local or imported pigments). Such information may shed some light on the artistic trends, the cultural purposes and the socio-economic (trading activity, importation of new techniques...) impacts of these artworks. However, Japanese prints are thin and complex artworks, made with various compounds: inorganic and/or organic pigments and dyes bound with rice starch, printed on Japanese paper (Figure 1). Japanese paper is itself a complex system whose preparation depends on the paper-

maker. Generally, various plant fibres are employed, like *kozo* or *gampi*. During the preparation, mineral fillers can be added, like calcium carbonate or white clay (kaolinite) in order to whiten the paper or increase its opacity. In addition, papers were sized with rice starch or *dosa* (animal skin glue and alum warmed in water) and sometimes dyed.¹⁴ For now, non-invasive methods have proven to be efficient for the identification of inorganic compounds but the identification of organic pigments remains a challenging task depending on their composition and concentration. In the case of paintings, NIR reflectance spectroscopy has been mainly employed for the identification of organic binders^{9,10} or of inorganic pigments.^{12,13} Thus we propose to evaluate the benefit of applying the NIR reflectance spectroscopy to probe traditional organic pigments used in Japanese *ukiyo-e* prints. For this purpose, analyses on reference isolated organic pigments and on model samples (colour chart) were performed. The main issues concerning the drawbacks of the techniques, such as the weakness of the pigment response and the overlapping of the NIR absorption bands (notably that originating from the paper substrate) will be discussed and a solution based on statistical treatment will be suggested.

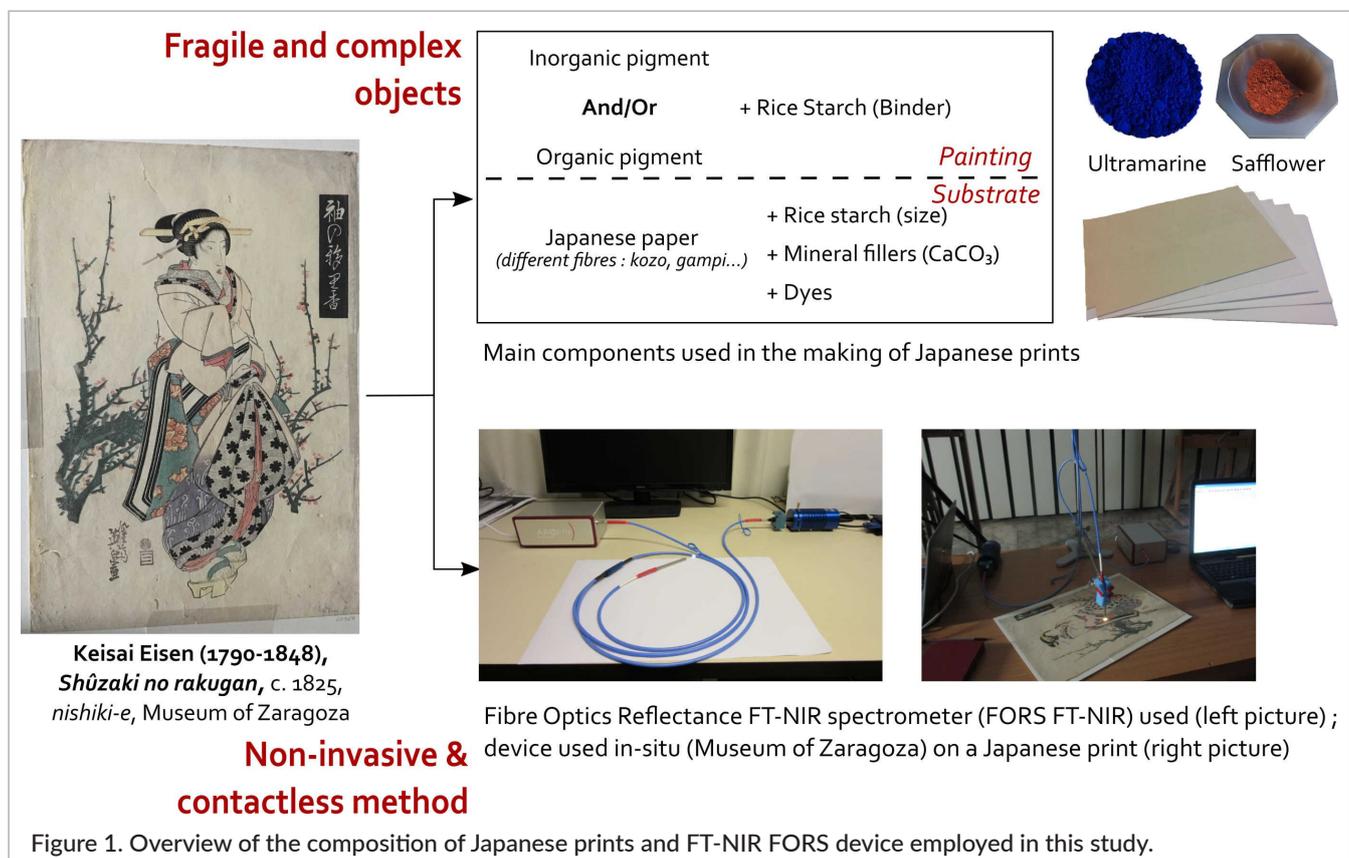


Figure 1. Overview of the composition of Japanese prints and FT-NIR FORS device employed in this study.

Materials and methods

Reference materials and colour chart

For this first approach, five organic pigments (indigo, safflower, gamboge, dragon's blood and cochineal), traditionally used in Asia,^{14,15} have been chosen for the building of a database dedicated to specific Japanese colouring matters in order to interpret future hyper-spectral data in the Short Wave InfraRed range (SWIR, 1000–2500 nm) of a collection of Japanese *ukiyo-e* prints. Their main chromophore molecules¹⁶ are shown in Figure 2. Indigo and safflower are obtained by extracting and precipitating the chromophores, from the leaves of *Persicaria tinctoria* or *Indigofera tinctoria* for indigo and from the flowers of *Carthamus tinctorius* for safflower. Gamboge and Dragon's blood are materials obtained from the exudate of the trees of the East-Asian genus *Garcinia* (for gamboge) and fruits of the *Daemenorops draco* (for dragon's blood). Contrary to the other pigments, the red soluble dye of cochineal (*Coccus cacti*), carminic acid, needs to be fixed onto an inorganic substrate to form an organo-metallic complex, such as aluminium or calcium salts, in order to produce the solid pigment.

A reference colour chart was prepared using the five colourants under consideration. They were used alone mixed with a drop of rice starch made in the laboratory using powder of rice starch provided by Kremer Pigmente according to the following proportions: 5 g of powder of rice starch for 100 mL of distilled water. The mixtures were applied on wooden blocks and printed on paper. The selected paper is made of 100% cellulose (without coating or sizing) in order to avoid any contribution from other fibres or additives on infrared spectra such as lignin or inorganic fillers. Paper was slightly moistened with distilled water prior to printing.

Near infrared spectroscopy

In order to collect the reflectance spectra in the NIR range, a portable ARCoPtix FT-NIR Rocket equipped with a photodiode InGaAs detector with a working range of 11,000–4000 cm⁻¹ (900–2500 nm) was used. The instrument is equipped with a HL2000 halogen lamp (Ocean Optics, 20 watts). Spectra were collected with an optical fibre bundle (Y shaped) which is constituted of seven optical fibres (fibre core size 400 μm, six illumination fibres around a collecting one; Figure 1). The measurement spot is of approximately 3 mm diameter.

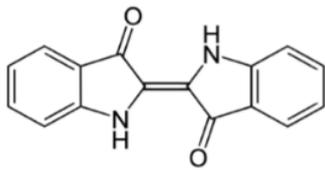
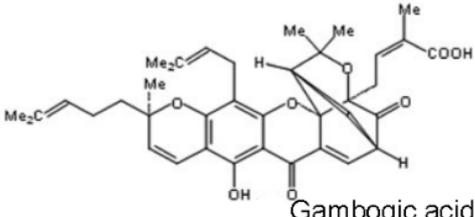
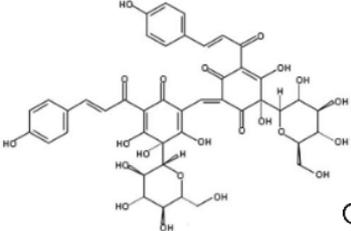
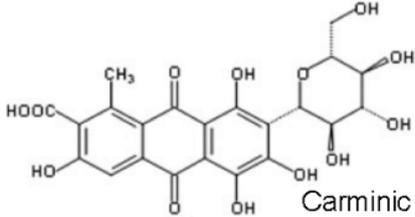
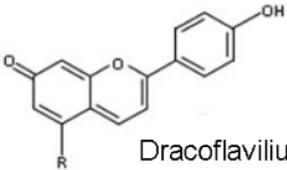
Organic pigment	Main chromophore
Indigo	 Indigotin
Gamboge	 Gambogic acid
Red Safflower	 Carthamin
Cochineal	 Carminic acid
Dragon's blood	 Dracoflavilium (R=OCH ₃)

Figure 2. List of the pigments and their main chromophores.

The probe was positioned perpendicularly to the surface thanks to a clamp standing at the end of an articulating arm, at a working distance ranging between 3 mm and 5 mm, in order to record the specular reflection component of the reflected light. Spectra were obtained by averaging 30 scans with an acquisition time about 20 s and at a 8 cm⁻¹ spectral resolution. The instrument was calibrated using a white Spectralon[®] standard.

Experimental approach

In the present work we applied infrared spectroscopy following two steps:

- Building of a database of isolated pigments in order to identify the characteristic spectral signatures for isolated colourants
- Investigation of a reference colour chart to characterise complex pigment/dyes mixtures printed on paper

Results and discussion

Isolated compounds

The first step consists in collecting reference spectra on neat standards (pigments, binder and substrate) in order to build a database of NIR spectra. Each isolated compound shows a specific signature in the NIR range (Figure 3). The paper and the rice starch are made of carbohydrates. The reference paper is made of 100% cellulose and its related bands are assigned mainly to OH groups: $2\nu(\text{OH})$ between 7000cm^{-1} and 6200cm^{-1} , combination of OH stretching and OH bending vibrations at about 5185cm^{-1} , principally due to adsorbed water, and combinations with CO stretching vibrations around 5495cm^{-1} [$\nu(\text{OH}) + 2\nu(\text{CO})$] and 4755cm^{-1}

[$\nu(\text{OH}) + \nu(\text{CO})$]. The other bands can be assigned to CH group vibrations: combination of CH stretching and CH bending vibrations at 7280cm^{-1} [$2\nu(\text{CH}) + \delta(\text{CH})$] and at 4275cm^{-1} [$\nu(\text{CH}) + \delta(\text{CH})$], first overtone of CH stretching vibration centred at 5600cm^{-1} and other combination bands between 4270cm^{-1} and 4000cm^{-1} .¹⁷ The spectrum of rice starch also presents bands ascribed to the carbohydrate signature between 7000cm^{-1} and 6200cm^{-1} [$2\nu(\text{OH})$], at 4775cm^{-1} [$\delta(\text{OH}) + \nu(\text{CO})$], between 6000cm^{-1} and 5600cm^{-1} [$2\nu(\text{CH})$] and between 4330cm^{-1} and 4000cm^{-1} (CH combination bands).¹⁷ The band at about 5170cm^{-1} [$\nu(\text{OH}) + \delta(\text{OH})$] is assigned to the presence of water.

Regarding the pigments, safflower is a red pigment composed of carthamin, a quinochalcone C-glycoside¹⁵ (Figure 2). Its NIR spectrum shows absorption regions corresponding to OH groups between 7000cm^{-1} and 6200cm^{-1} [$2\nu(\text{OH})$] and at 5170cm^{-1} [$\nu(\text{OH}) + \delta(\text{OH})$] which are mainly assigned to water. A pattern visible at about 5780cm^{-1} is correlated to the first CH stretching overtones and the bands observed at 4330cm^{-1} and 4250cm^{-1} are due to CH stretching and CH bending combinations, which is consistent with the intense CH stretching mode measured in the mid-infrared spectrum.¹ The spectrum of cochineal is characterised by weak

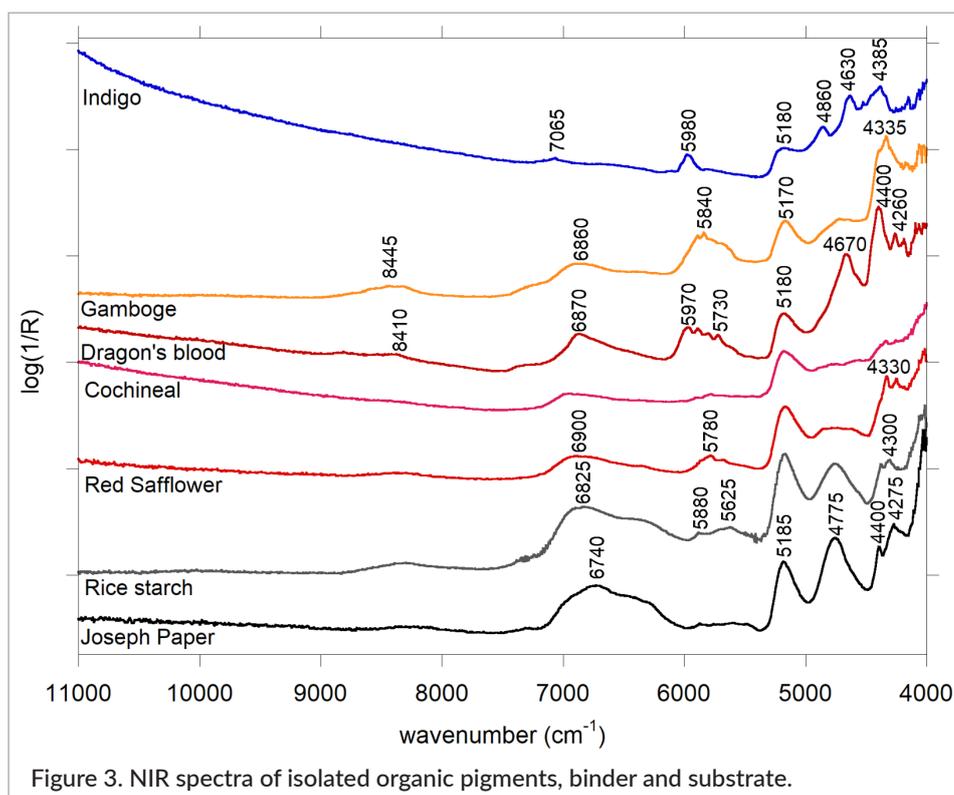


Figure 3. NIR spectra of isolated organic pigments, binder and substrate.

bands mainly at 6955 cm^{-1} [$2\nu(\text{OH})$], between 5900 cm^{-1} and 5600 cm^{-1} [$2\nu(\text{CH})$] and at 4330 cm^{-1} and 4260 cm^{-1} [$\nu(\text{CH}_2) + \delta(\text{CH}_2)$].¹⁷

Gamboge and dragon's blood are complex mixtures of several molecules including chromophores such as gambogic acid and dracoflavilium (Figure 2) as well as gum and/or resin components.^{14,18} The spectra of both pigments are characterised by absorption bands of CH groups. The first and second overtones of CH stretching vibrations are observed, respectively, between 6100 cm^{-1} and 5500 cm^{-1} , very specific for dragon's blood with four defined absorption bands (5970 , 5890 , 5805 and 5730 cm^{-1}), and between 9000 cm^{-1} and 8000 cm^{-1} . The combination bands are located at about 7300 cm^{-1} and between 4350 cm^{-1} and 4000 cm^{-1} . The broad absorption between 7000 cm^{-1} and 6200 cm^{-1} is ascribed to the first overtone of OH stretching vibrations. The bands centred at 5170 cm^{-1} for gamboge and at 5180 cm^{-1} for dragon's blood are assigned to OH stretching and bending combination. The dragon's blood spectrum also exhibits a specific band at 4670 cm^{-1} that can be assigned to the CO stretching and CH_2 stretching combination.^{9,17}

The spectrum of indigo exhibits several narrow but weak bands. Among them, the bands at 7065 , 5180 and 4630 cm^{-1} are not ascribed to indigo but to kaolinite [$\text{Al}_2\text{Si}_2\text{O}_5(\text{OH})_4$]¹⁹ which may be used as an extender in order to increase the quantity or the bulk of the

pigment or to modify its colour. This result has been confirmed by energy-dispersive x-ray spectroscopy (EDXS) analyses that indicate the presence of silicon and aluminium. The other bands are due to the molecule of indigo. The band centred around 5980 cm^{-1} is assigned to the first overtone of CH group stretching vibrations. In addition, combinations of CH group vibrations are certainly involved in numerous narrow bands between 4700 cm^{-1} and 4000 cm^{-1} . Finally, the band located at about 4860 cm^{-1} is ascribed to the combination of NH stretching and bending vibrations.²⁰

Reference colour chart

A colour chart of paints printed on paper was prepared in order to study mixtures of pigment and binder on paper mimicking the real case of Japanese prints. The NIR spectra of the depositions mainly present the spectral signatures of the paper substrate and the rice starch (Figure 4) with bands located at about 6750 , 5185 , 4760 and 4400 cm^{-1} . For the pigments, only few spectral features can be distinguished on the spectra of dragon's blood, gamboge and indigo (indicated by arrows) due to overlapping bands of the paper and the starch.

Statistical methods can be used to explore further the infrared data in order to extract information from the spectra. In this first approach, Principal Component Analysis (PCA) was applied to discriminate and identify


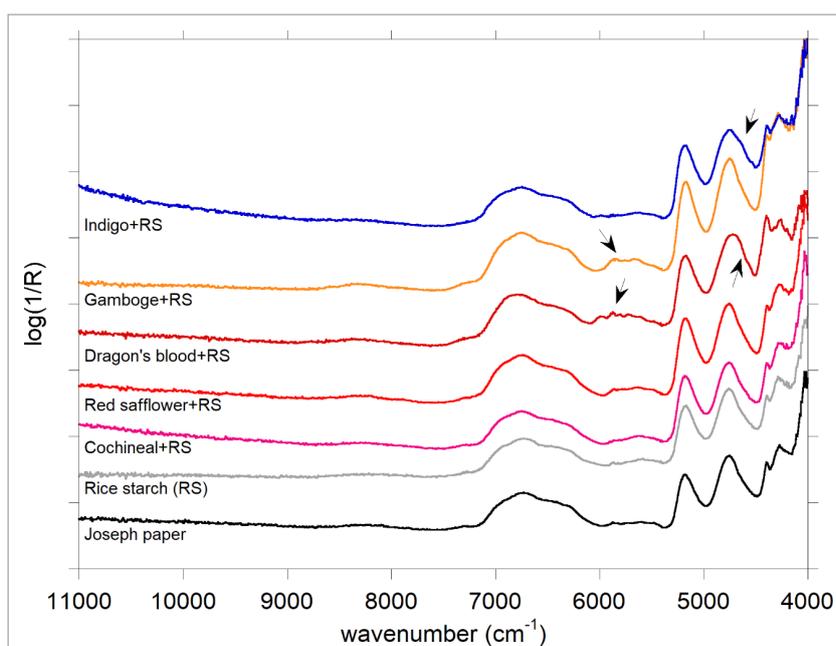


Figure 4. NIR spectra of painted layers with organic pigments on the reference colour chart.

the pigments used in the mixtures on the depositions. Eight spectra have been acquired on each deposition on the colour chart for a total data set of 40 spectra. Data were pre-treated with first derivative Savitzky-Golay algorithm (polynomial order 1, 11 data points) followed by Standard Normal Variation (SNV) in the range 4100–8500 cm^{-1} (Figure 5a and b). The first four principal components (PC) calculated by the statistical model explain a percentage of 92% of variability (PC1: 51.3%, PC2: 20.4%, PC3: 14% and PC4: 6.5%). The score plots of the PC1 against the PC2 and the PC1 against the PC4 are reported in Figure 5c and 5d. They show that the deposition made with dragon's blood can be clearly distinguished from the others thanks to PC1. Following the loading plots (not shown here), the vibrations that contribute to the PC1 are mainly due to those of dragon's blood with the well-defined and specific absorptions of the first overtones of the CH stretching vibrations between 6000 cm^{-1} and 5500 cm^{-1} as well

as the CO stretching and CH_2 stretching combination at about 4660 cm^{-1} . The two score plots show that the depositions of safflower and cochineal are sparse and not well separated whereas the depositions of indigo and gamboge are, respectively, grouped. The vibrations of paper and rice starch strongly contribute to the PC2 loading plot (around 5200 cm^{-1} and 4765 cm^{-1}) but features assigned to gamboge can be highlighted in the region of the first overtones of CH stretching vibrations (5900–5500 cm^{-1}). In the case of the deposition of indigo, the discrimination can be clearly made thanks to the PC4 (Figure 5d) with the contribution of the characteristic vibrations of the molecule of indigo at about 5980 cm^{-1} and 4850 cm^{-1} but also of the extender kaolinite (around 7050 cm^{-1}). The discrimination of safflower and cochineal still remains difficult as their NIR absorption bands are located in the same ranges as those of paper and starch (7000–6200 cm^{-1} and 5180 cm^{-1}) and due to the weakness of their

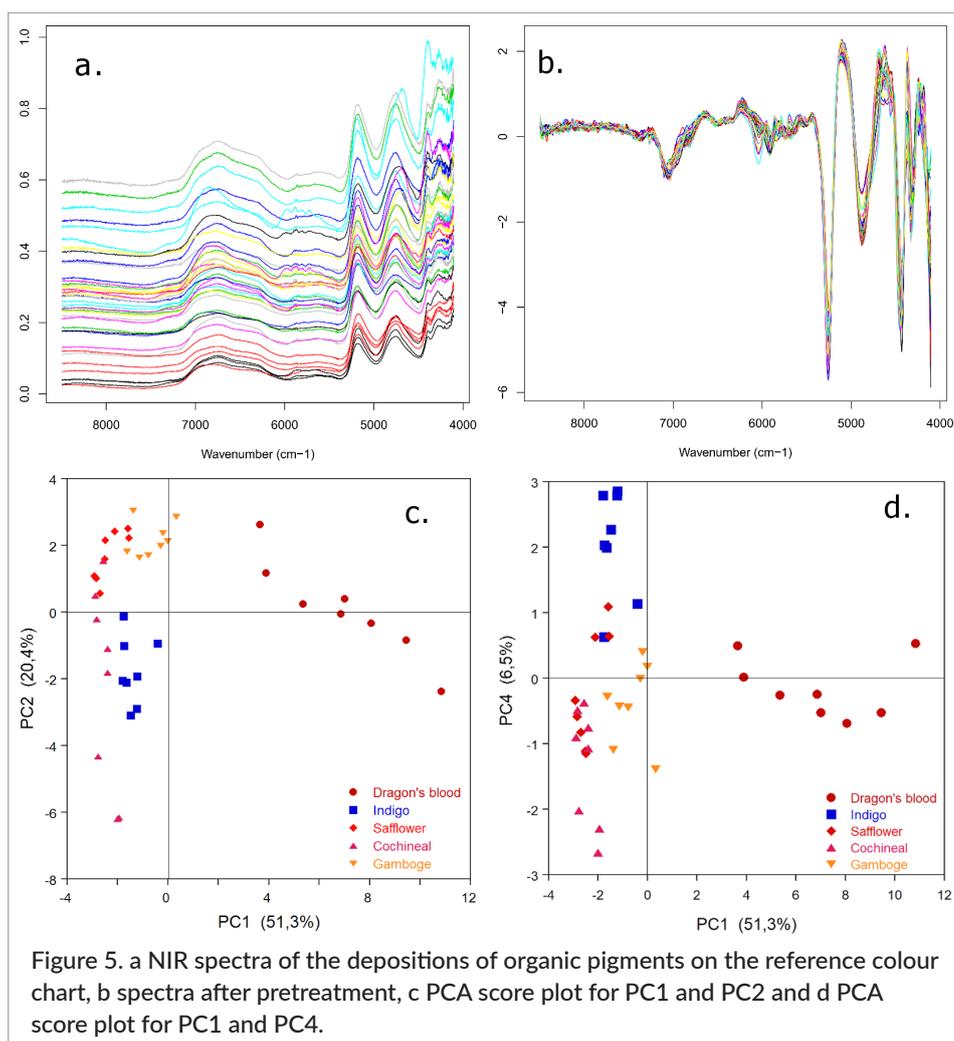

specific absorptions ($6000\text{--}5600\text{ cm}^{-1}$ and 4330 cm^{-1} and 4260 cm^{-1}).

Conclusion

Portable NIR spectroscopy has been used for the first time on a set of five traditional Asian organic pigments involved in Japanese woodblock prints. Dragon's blood, indigo and gamboge pigments exhibit very specific bands in this range. However, in the case of paint deposition (mixture of pigment and binder) on paper substrate, the discrimination between the pigments appears difficult due to the overlapping spectral signatures of the paper and the rice starch. Chemometric treatments such as Principal Component Analysis has been considered in order to explore the data. For now, we highlight the possibility to discriminate between dragon's blood, gamboge and indigo depositions and suggest the use of spectral regions of interest, mainly related to the CH overtone and combination modes. Results also emphasise the importance of carefully paying attention to spectral contribution of each component in the building of the PCs. Indeed, pigments and more importantly paints are complex mixtures and in some instance, as it is the case for indigo, not only the chromophore molecule but also inorganic additives, which are not specific of the pigment, might be considered in the model. The pre-treatment of the data may be improved and other data processing schemes may be considered in the future such as clustering methods (Hierarchical cluster analysis, fuzzy C-means analysis)²¹ or the combination of specific NIR ranges with other spectral domains (mid-infrared range or Raman) in the statistical model which has been proved relevant for the discrimination of organic binders.^{10,22}

Acknowledgement

This project (INDIGO, coord. F. Daniel) was supported by the University Bordeaux Montaigne and University of Bordeaux, the French State managed by the French National Research Agency within the framework of the cluster of excellence *Laboratoire des Sciences Archéologiques de Bordeaux* (ANR-10-LABX-52) and the CNRS.

We also acknowledge the International Council for Near Infrared Spectroscopy (ICNIRS) for supporting this work through the John Shenk Travel Grant.

References

1. C. Biron, G. Le Bourdon, J. Pérez-Arantegui, L. Servant, R. Chapoulie and F. Daniel, "Probing some organic ukiyo-e Japanese pigments and mixtures using non-invasive and mobile infrared spectroscopies", *Anal. Bioanal. Chem.* **410**, 7043–7054 (2018). <https://doi.org/10.1007/s00216-018-1305-2>
2. M. Leona and J. Winter, "The identification of indigo and prussian blue on Japanese edo-period paintings", in *Studies using Scientific Methods. Pigments in Later Japanese Paintings*. Freer Gallery of Art, Occasional Papers, Smithsonian Institution, Washington, DC, USA (2003).
3. S. Pessanha, M. Manso and M.L. Carvalho, "Application of spectroscopic techniques to the study of illuminated manuscripts: a survey", *Spectrochim. Acta B* **71–72**, 54–61 (2012). <https://doi.org/10.1016/j.sab.2012.05.014>
4. A. Mounier, G. Le Bourdon, C. Aupetit, C. Belin, L. Servant, S. Lazare, Y. Lefrais and F. Daniel, "Hyperspectral imaging, spectrofluorimetry, FORS and XRF for the non-invasive study of medieval miniatures materials", *Heritage Sci.* **2**, 24–36 (2014). <https://doi.org/10.1186/s40494-014-0024-z>
5. F. Daniel, A. Mounier, J. Perez-Arantegui, N. Prieto-Taboada, S. Fdez-Ortiz de Vallajuelo and K. Castro, "Hyperspectral imaging applied to the analysis of Goya paintings in the Museum of Zaragoza (Spain)", *Microchem. J.* **126**, 113–120 (2016). <https://doi.org/10.1016/j.microc.2015.11.044>
6. S. Bruni, E. De Luca, V. Guglielmi and F. Pozzi, "Identification of natural dyes on laboratory-dyed wool and ancient wool, silk, and cotton fibers using attenuated total reflection (ATR) Fourier transform infrared (FT-IR) spectroscopy and Fourier transform Raman spectroscopy", *Appl. Spectrosc.* **65**, 1017–1023 (2011). <https://doi.org/10.1366/10-06203>
7. C. Miliani, F. Rosi, I. Borgia, P. Benedetti, B.G. Brunetti and A. Sgamellotti, "Fiber-optic Fourier transform mid-infrared reflectance spectroscopy: a suitable technique for *in situ* studies of mural paint-

- ings", *Appl. Spectrosc.* **61**, 293–299 (2007). <https://doi.org/10.1366/000370207780220840>
8. M. Manfredi, E. Barberis, M. Aceto and E. Marengo, "Non-invasive characterization of colorants by portable diffuse reflectance infrared Fourier transform (DRIFT) spectroscopy and chemometrics", *Spectrochim. Acta A* **181**, 171–179 (2017). <https://doi.org/10.1016/j.saa.2017.03.039>
 9. M. Vagnini, C. Miliani, L. Cartechini, P. Rocchi, B.G. Brunetti and A. Sgamellotti, "FT-NIR spectroscopy for non-invasive identification of natural polymers and resins in easel paintings", *Anal. Bioanal. Chem.* **395**, 2107–2118 (2009). <https://doi.org/10.1007/s00216-009-3145-6>
 10. A. Pallipurath, J. Skelton, P. Ricciardi, S. Bucklow and S. Elliott, "Multivariate analysis of combined Raman and fibre-optic reflectance spectra for the identification of binder materials in simulated medieval paints", *J. Raman Spectrosc.* **44**, 866–874 (2013). <https://doi.org/10.1002/jrs.4291>
 11. V. Šuštar, J. Kolar, L. Lusa, T. Learner, M. Schilling, R. Rivenc, H. Khanjian and D. Koleša, "Identification of historical polymers using near-infrared spectroscopy", *Polym. Degrad. Stabil.* **107**, 341–347 (2014). <https://doi.org/10.1016/j.polymdegradstab.2013.12.035>
 12. M. Aceto, A. Agostino, G. Fenoglio, A. Idone, M. Gulmini, M. Picollo, P. Ricciardi and J.K. Delaney, "Characterisation of colourants on illuminated manuscripts by portable fibre optic UV-visible-NIR reflectance spectrophotometry", *Anal. Methods* **6**, 1488–1500 (2014). <https://doi.org/10.1039/c3ay41904e>
 13. S. Kogou, A. Lucian, S. Bellesia, L. Burgio, K. Bailey, C. Brooks and H. Liang, "A holistic multimodal approach to the non-invasive analysis of watercolour paintings", *Appl. Phys. A* **121**, 987–1002 (2015). <https://doi.org/10.1007/s00339-015-9425-4>
 14. J. Winter, *East Asian Paintings. Materials, Structures and Deterioration Mechanisms*. Archetype Publications, London, UK (2008).
 15. D. Cardon, *Le Monde des Teintures Naturelles*. Belin, Paris, France (2014).
 16. S. Bruni, V. Guglielmi and F. Pozzi, "Historical organic dyes: a surface-enhanced Raman scattering (SERS) spectral database on Ag Lee-Meisel colloids aggregated by NaClO₄", *J. Raman Spectrosc.* **42**, 1267–1281 (2011). <https://doi.org/10.1002/jrs.2872>
 17. J. Workman and L. Weyer, *Practical Guide and Spectral Atlas for Interpretative Near-Infrared Spectroscopy* (2nd Edn). CRC Press, Taylor & Francis Group, Boca Raton, USA (2012).
 18. D. Gupta, B. Bleakley and R.K. Gupta, "Dragon's blood: botany, chemistry and therapeutic uses", *J. Ethnopharmacol.* **115**, 361–380 (2008). <https://doi.org/10.1016/j.jep.2007.10.018>
 19. R.F. Kokaly, R.N. Clark, G.A. Swayze, K.E. Livo, T.M. Hoefen, N.C. Pearson, R.A. Wise, W.M. Benzel, H.A. Lowers, R.L. Driscoll and A.J. Klein, *USGS Spectral Library Version 7*. U.S. Geological Survey Data Series 1035 (2017). <https://doi.org/10.3133/ds1035>
 20. C. Tsiantos, M. Tsampodimou, G.H. Kacandes, M.S. del Río, V. Gionis and G.D. Chryssikos, "Vibrational investigation of indigo-palygorskite association(s) in synthetic Maya blue", *J. Mater. Sci.* **47**, 3415–3428 (2012). <https://doi.org/10.1007/s10853-011-6189-x>
 21. A. Rammal, E. Perrin, V. Vrabie, I. Bertrand and B. Chabbert, "Classification of lignocellulosic biomass by weighted-covariance factor fuzzy C-means clustering of mid-infrared and near-infrared spectra", *J. Chemometr.* **31**, e2865 (2017). <https://doi.org/10.1002/cem.2865>
 22. S. Carlesi, M. Becucci and M. Ricci, "Vibrational spectroscopies and chemometry for non-destructive identification and differentiation of painting binders", *J. Chem.* 3475659 (2017). <https://doi.org/10.1155/2017/3475659>